




VUV Reflectance Measurements for Materials Relevant to Argon and Xenon Experiments


J. Soto-Otón (UvA/Nikhef), H. Amar, A. Cervera, A. Roche (IFIC-CSIC/UV)

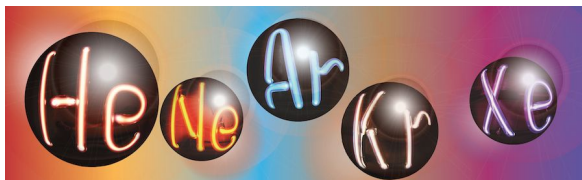



Reflectance measurements at IFIC

- Optical measurements in the **vacuum ultraviolet** are crucial for a better understanding and **optimization of the photon detection**.
- **Reflectance values** are essential for estimating an accurate light yield for any noble gas detector. In particular, important materials in DUNE are aluminum (Field cage) and stainless steel (cryostat).
- **Reflectance directly affects the light yield and the PDE estimation**. It is crucial to have dedicated measurements to ensure accurate results.
- Reflectance values for VUV light are not well known. Different values can be found in the literature, and **highly depends on the sample** (surface treatment and/or termination).
- At IFIC, we have **dedicated a setup to perform angular-resolved reflectance measurements in the VUV range**. This setup includes calibrated samples to validate the method and measurements of real cryostat and field cage samples from DUNE.
- Additionally, an angular-resolved measurement would allow to improve our understanding of the photon propagation inside the detector, and **refine the simulation implementing an angular distribution**.

Detected light vs distance per muon track in ProtoDUNE-DP (simulation)

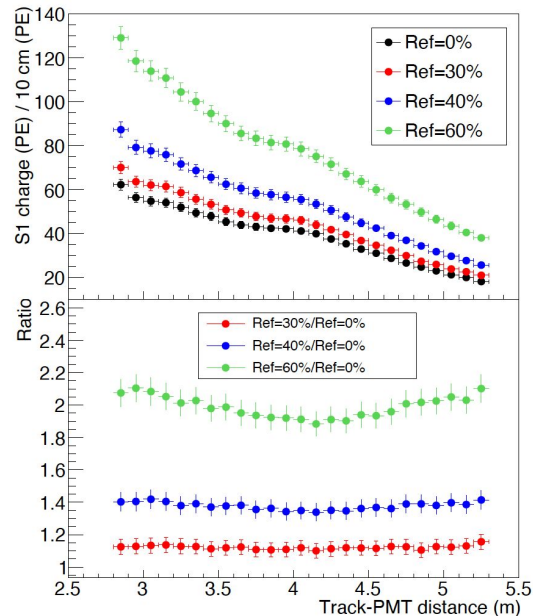

VUV optical measurements in a GAr atmosphere

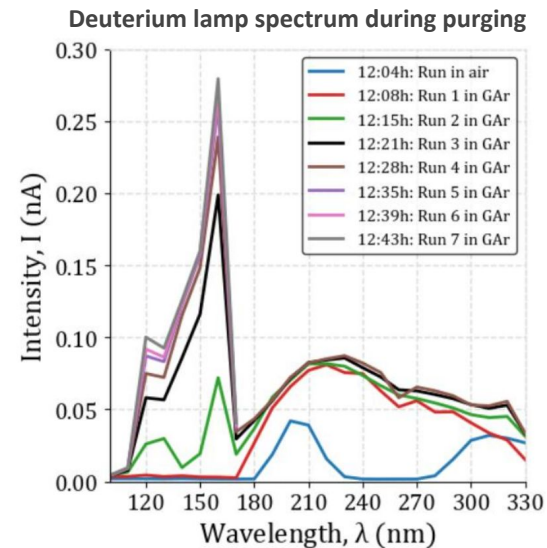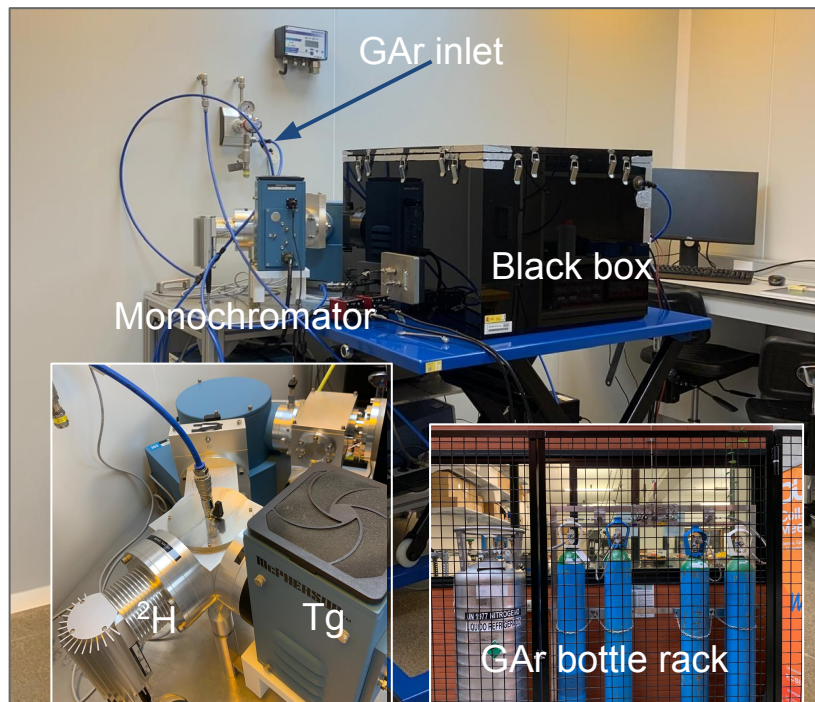



- A D₂ lamp coupled to a monochromator and connected to a GAr system in a dedicated dark room.
- Measurements are conducted in a pure GAr atmosphere to enable light transmission in the VUV region.
- The spectrum of the D₂ lamp during purging is shown above.
- Using a GAr atmosphere:
 - Protects the monochromator grating from outgassing.
 - **Provide flexibility to fully instrument the black box.**

A setup for angular-resolved measurements

- A 3D-printed assembly that contains two Thorlabs rotary stages and a motorized sample holder.
 - Motor 1: To change samples.
 - Motor 2: To rotate a VUV-sensitive PMT.
 - Motor 3: To rotate the sample holder.
- Additionally, an iris + shutter.
- A rectangular mask of $2 \times 20 \text{ mm}^2$ for the PMT, with an opening of 0.8° , is employed to enhance angular resolution.

This automated setup enables the measurement of light angular distributions at various angles of incidence (AOI) and samples.

- **DUNE Aluminum field cage profiles.**
- **DUNE Stainless steel cryostat membrane.**

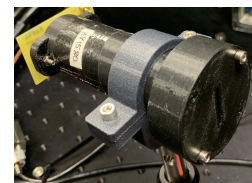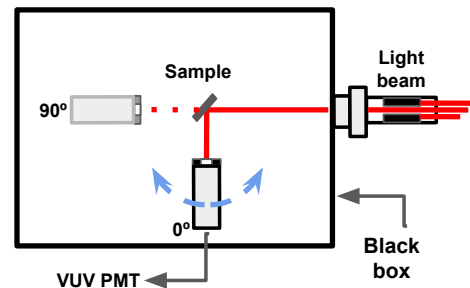



PMT with mask



Sample holder



Reflectance measurements

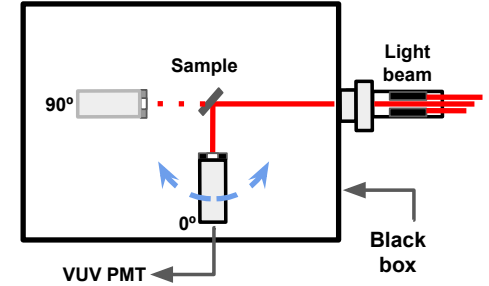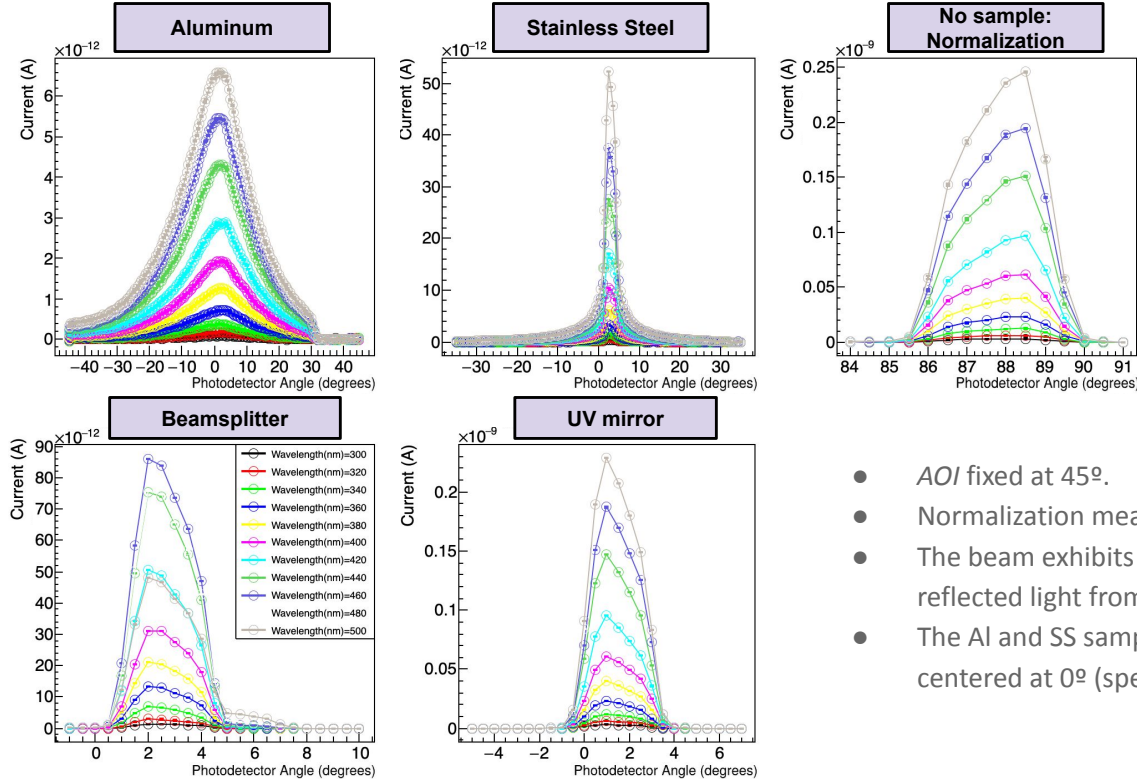



- AOI fixed at 45°.
- Normalization measurement taken for every wavelength.
- The beam exhibits an asymmetrical profile, which is evident in the reflected light from the specular samples.
- The Al and SS samples exhibit a broad distribution (diffuse-like) centered at 0° (specular-like).

Measurements at different angles of incidence

- An ideal reflector would exhibit a Lambertian distribution.
- The samples under study demonstrate a hybrid distribution that aligns well with this equation derived from the Phong model [1]:

$$\sum A_i (\cos(x - x_0))^{n_i}$$



- The parameter n corresponds to the surface termination.

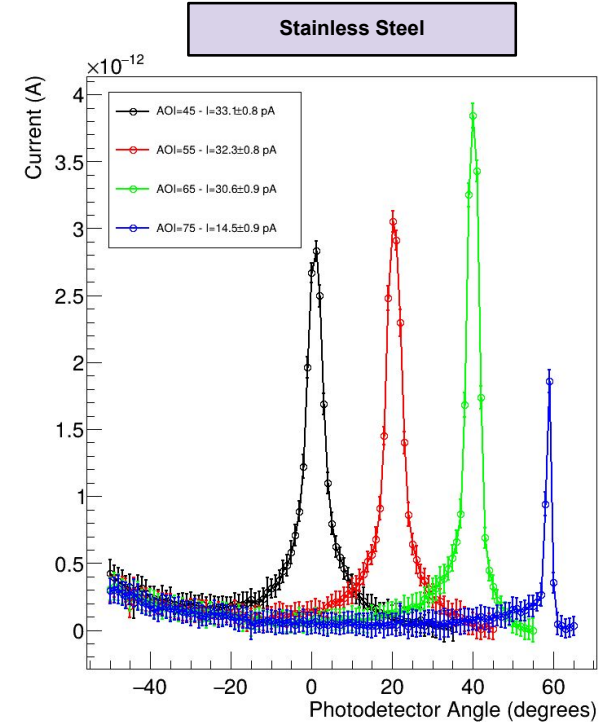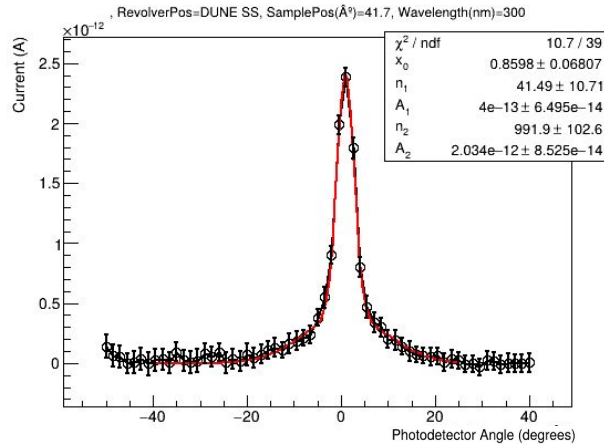

[1] Phong, Bui Tuong. Illumination for Computer Generated Pictures. Communications of the ACM, 18(6), 1975, (pp. 311-317.)




Reflectance measurements using Tg lamp (300-500nm)

- Reflectance is obtained by integrating the angular resolved measurement, and dividing by the normalization.
- A correction is applied to diffuse samples (Al and SS), assuming angular symmetry, to estimate the light not collected in the scan (at wide angles).
- Control samples (mirror and beamsplitter) reproduce well the reference values.
- Reflectance measurements indicate approximately 70% for aluminum and 40% for stainless steel in the UV-VIS region.

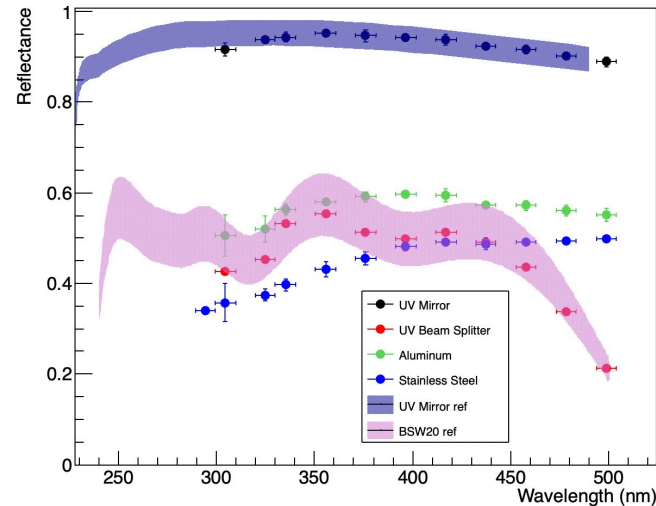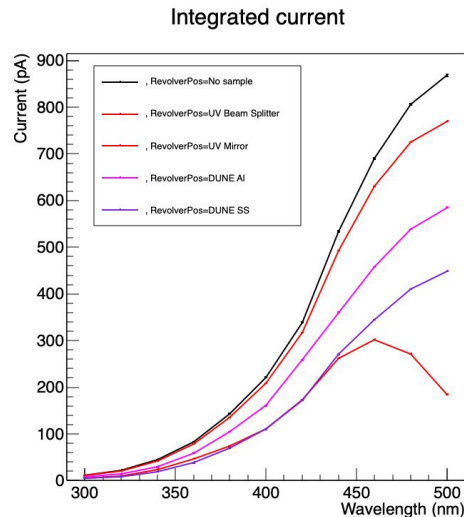


Reflectance measurements using D₂ lamp in GAr (VUV)

- Despite the small signal, we have successfully detected reflected light in the VUV spectrum for both samples.
- Normalization measurements are taken before and after each sample, to ensure the atmosphere transmission is stable.
- Stainless-steel reflects more specularly.

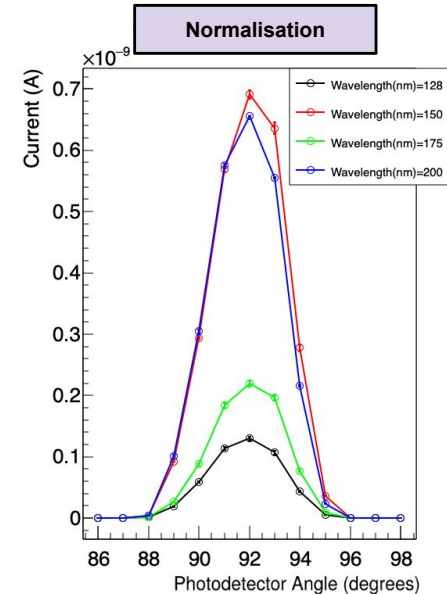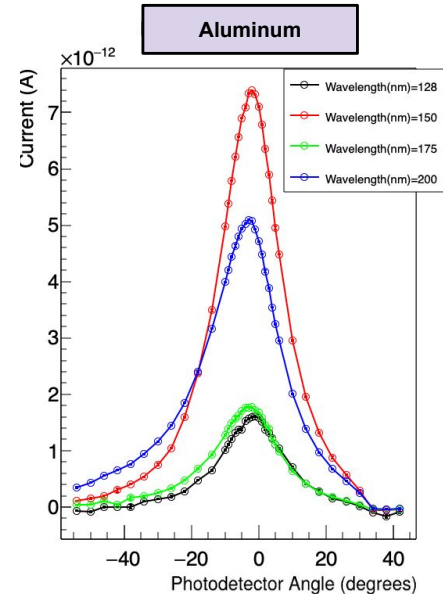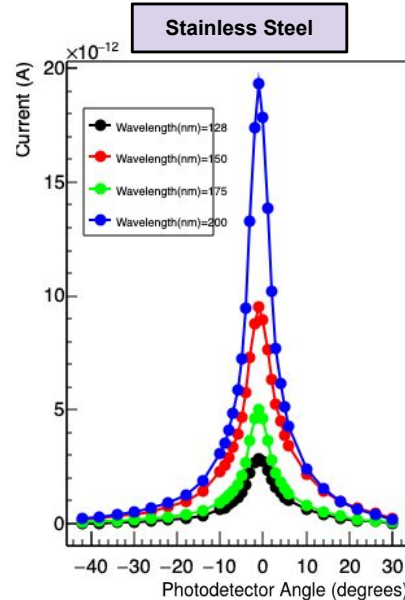



Reflectance measurements using D₂ lamp in GAr (VUV)

- Angular distribution looks very similar at different wavelengths.
- Aluminum seems to be slightly more specular at shorter wavelengths.
- Normalization measurements points to a light **transmission stability** through the GAr atmosphere better than 6%.

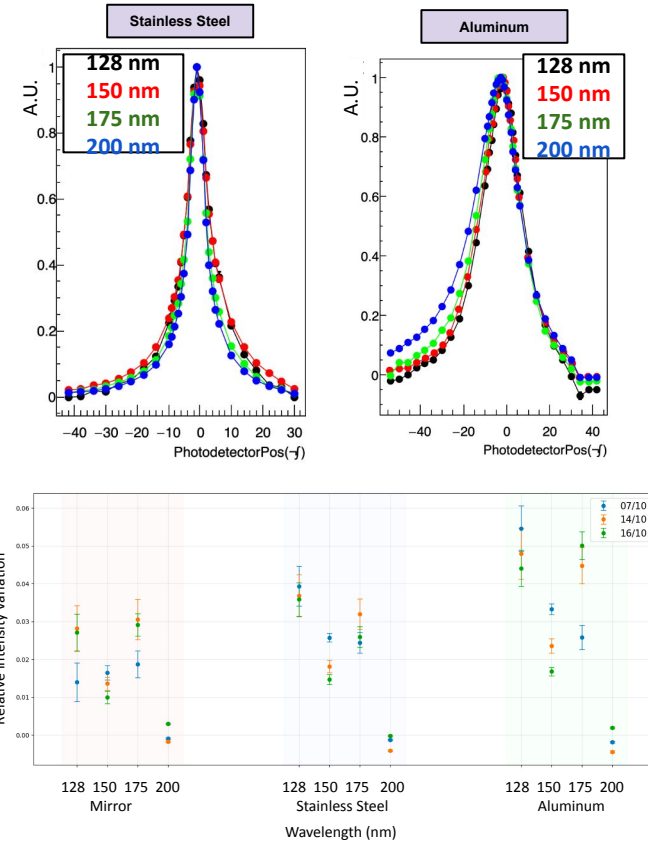


Aluminum and Stainless steel reflectance in the VUV

- Reflectance measurements for Al and SS indicate approximately 10-15% at 45°.
- A better **understanding of the systematics** is currently being investigated:
 - Effect of the GAr atmosphere stability.
 - Beam size and collimation (iris).
 - Extrapolation to 2π .

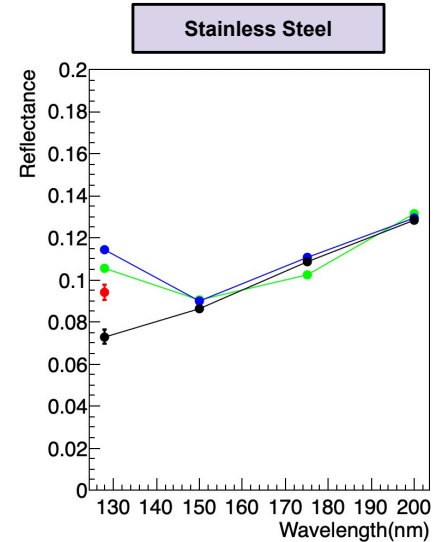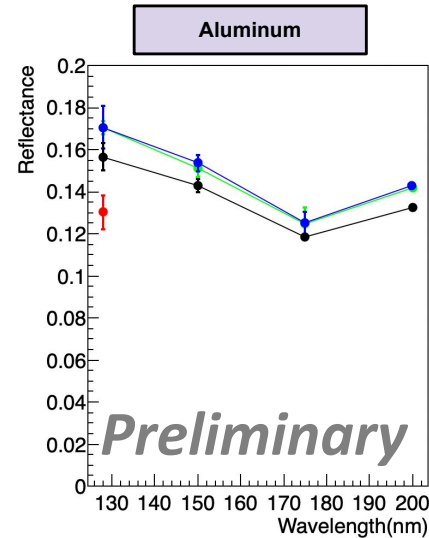

Summary of results and next steps

- A setup to performed optical measurements in the VUV range using a gaseous argon atmosphere is available at IFIC.
- The system allows to perform sophisticated measurements that would be more challenging in vacuum.
- Preliminary measurements points to reflectivity values in the range of 10-15% for aluminum and stainless steels samples.
- Better understanding of the systematics is under study.

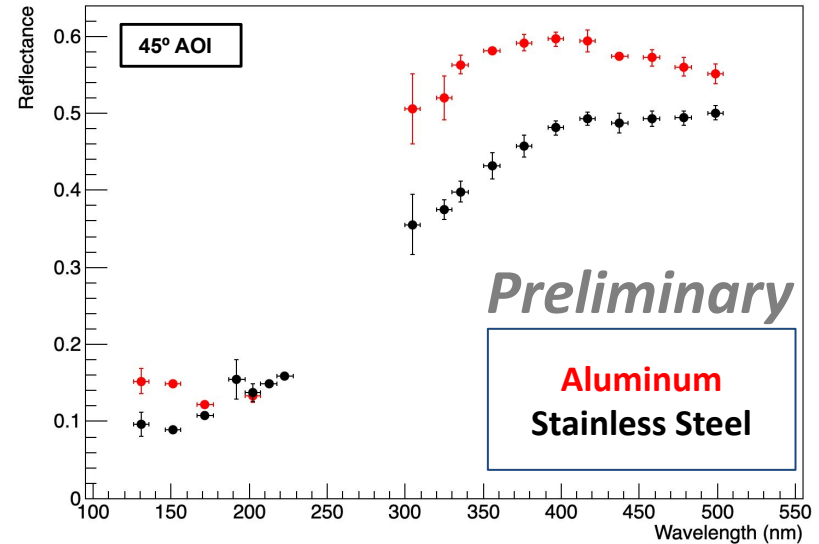


Backup

A Ring model to extract the integrated emitted light

- In diffuse samples, light is emitted in a 2π pattern, and the PMT does not collect all light.
- By assuming radial symmetry, we can correct for the non-collected light.
- If the PMT is covered with a mask of known size M , a simple ring model can be proposed: $I_i = \sum_j A_j \cap M_i F_j$


Variable	Definition	Units	Comment
I_i	Current in position i .	A	Our data.
A_j	Area of the j ring.	m ²	Intersection can be solved analytically.
M_i	Mask area at i position.	m ²	
F_j	Average photo-current density in the whole ring.	A/m ²	Obtained by fitting the data.

$$\text{Total emitted light} = \sum_j A_j F_j$$

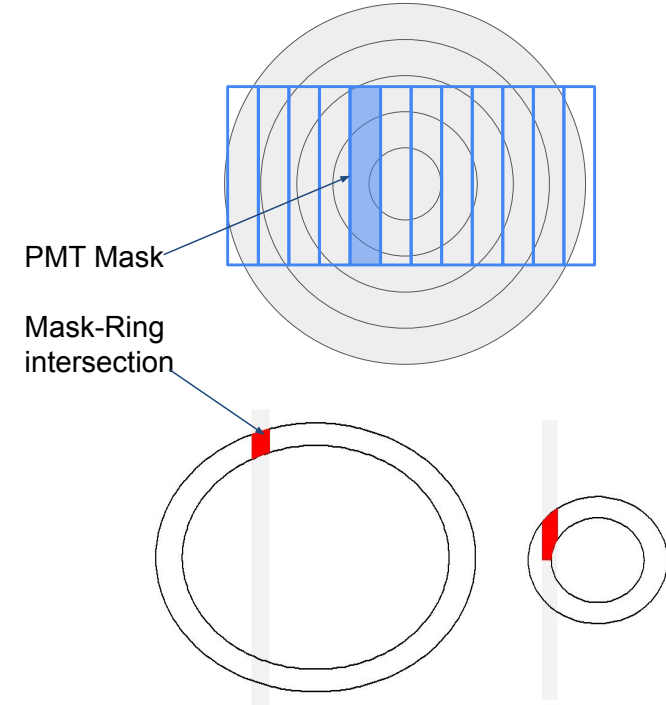


The Ring model performance


Stainless Steel, 41.7, 320, $I = 27.4 \pm 0.5$ pA

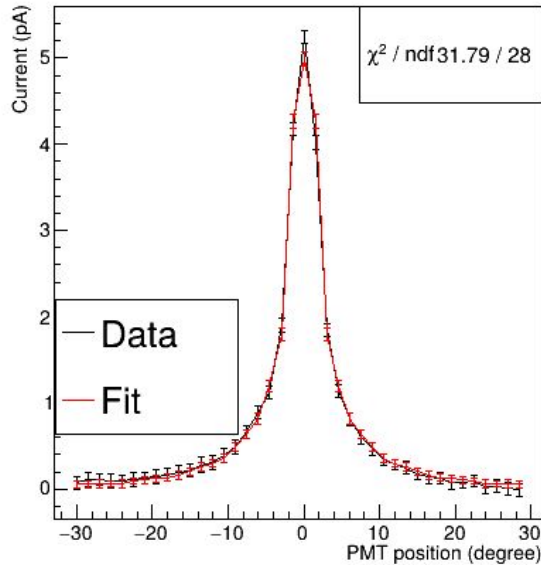

F: Current density for each ring

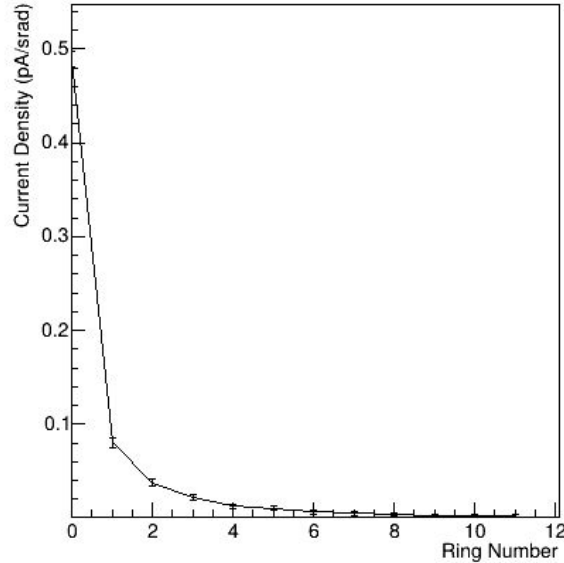

$\Sigma F \cdot A = 35.42 \pm 2.08$ pA

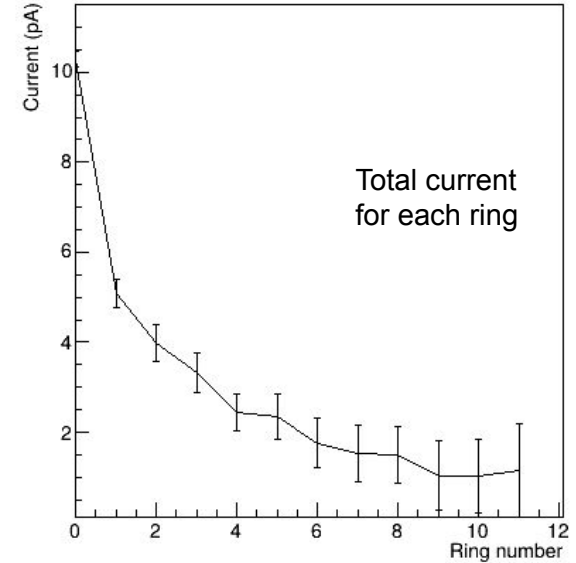

- The model adheres to the requirement of symmetry.
- It provides an estimation of the total emitted light, which is 50% higher than the directly measured value.
- However, the error associated with this estimation is also increased.

O₂ molecular absorption in the UV-VUV range

